

AD-A073 130

TEXAS UNIV AT AUSTIN DEPT OF CHEMISTRY

F/G 7/3

SPECTRAL SENSITIZATION OF THE HETEROGENEOUS PHOTOCATALYTIC OXID--ETC(U)

AUG 79 F F FAN, A J BARD

N00014-78-C-0592


UNCLASSIFIED

TR-1

NL

AD
A073 30


AD



END
DATE
FILMED

79

DDC

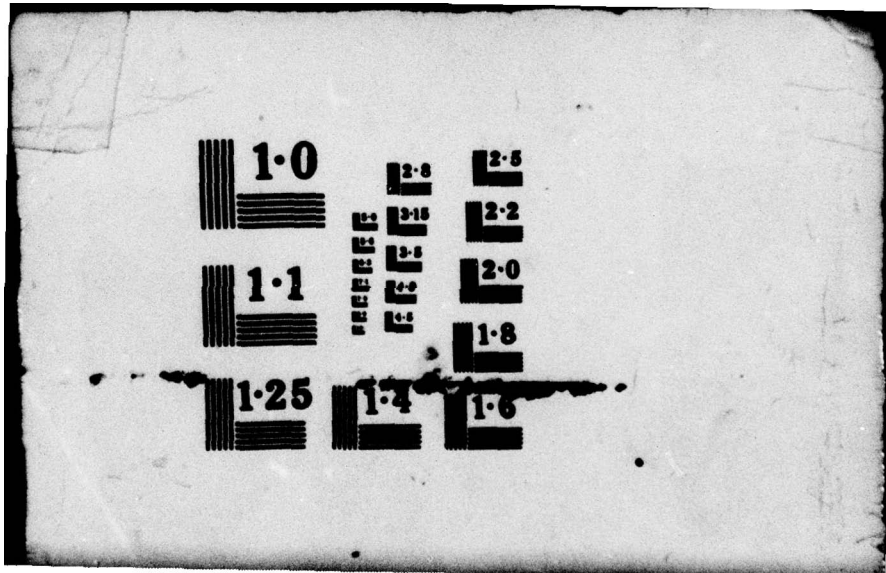

LEVEL

12

OFFICE OF NAVAL RESEARCH

Contract N00014-78-C-0592

Task No. NR 051-693

AD A 073130

9

TECHNICAL REPORT

1 Sep 78 - 31 Aug 79

6

Spectral Sensitization of the Heterogeneous
Photocatalytic Oxidation of Hydroquinone in
Aqueous Solutions at Phthalocyanine-Coated
 TiO_2 Powders •

by

10

Fu-Ren F./Fan Allen J./Bard

Prepared for Publication

in the

Journal of the American Chemical Society

15 N00014-78-C-0592

14 TR-1

DDC
REF ID: A66116
AUG 21 1979
REGISTERED

The University of Texas at Austin
Department of Chemistry
Austin, Texas 78712

11

1 August 1979

12 15p.

DDC FILE COPY

Reproduction in whole or in part is permitted for
any purpose of the United States Government.

This document has been approved for public release
and sale; its distribution is unlimited.

347 830

79 08 20 022

JOB

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 1	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) SPECTRAL SENSITIZATION OF THE HETEROGENEOUS PHOTOCATALYTIC OXIDATION OF HYDROQUINONE IN AQUEOUS SOLUTIONS AT PHTHALOCYANINE-COATED TiO ₂ POWDERS		5. TYPE OF REPORT & PERIOD COVERED 1 Sept. 1978 to 31 Aug. 1979
7. AUTHOR(s) Fu-Ren F. Fan and Allen J. Bard		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry University of Texas at Austin Austin, TX 78712		8. CONTRACT OR GRANT NUMBER(s) N00014-78-C-0592
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research 800 N. Quincy Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE August 1, 1979
		13. NUMBER OF PAGES 16
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release and sale; its distribution is unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Prepared for publication in the Journal of the American Chemical Society.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) phthalocyanine photoelectrochemistry heterogeneous photocatalysis		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The photocatalyzed reaction of hydroquinone with oxygen at TiO ₂ (anatase) powders coated with metal-free or magnesium phthalocyanine under irradiation with light of energy less than the TiO ₂ band gap is described. The behavior at the powders is correlated with current-potential curves at single crystal n-type TiO ₂ electrode and an energy level scheme for the reaction is proposed.		

Spectral Sensitization of the Heterogeneous
Photocatalytic Oxidation of Hydroquinone in
Aqueous Solutions at Phthalocyanine-Coated
 TiO_2 Powders

(ABSTRACT)

The photocatalyzed reaction of hydroquinone with oxygen at TiO_2 (anatase) powders coated with metal-free or magnesium phthalocyanine under irradiation with light of energy less than the TiO_2 band gap is described. The behavior at the powders is correlated with current-potential curves at single crystal n-type TiO_2 electrodes and an energy level scheme for the reaction is proposed.

(End of Abstract)

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or special
<input checked="checked" type="checkbox"/>	

Spectral Sensitization of the Heterogeneous
Photocatalytic Oxidation of Hydroquinone in
Aqueous Solutions at Phthalocyanine-Coated
 TiO_2 Powders

Sir:

Recent investigations have described the application of the principles of semiconductor electrodes to the design of large surface area powders that serve as photocatalysts for reactions of fundamental and practical interest.¹ These photocatalysts were generally materials with wide band gaps and thus they only absorb a small fraction of the available sunlight. However photo-active dyes can be either adsorbed or covalently attached to semiconductor electrode surfaces to sensitize the electrode to visible wavelength light and thus produce photocurrents or photovoltages at longer wavelengths.²⁻¹⁴ We were intrigued by the possibility that dye-coated semiconductor powders could be employed as useful sensitized heterogeneous photocatalysts with an improved response to visible light. The phthalocyanines appear most appropriate for this study because (1) they are chemically very stable, (2) they have highly absorbing chromophores within the solar spectrum, (3) they have moderately high electrical conductivity so that reasonably thick films with good optical absorption can be prepared, and (4) their redox potentials can be varied by changes in the central metal. To our knowledge spectral sensitization of semiconductor powders has not yet been demonstrated, although Uchida, *et. al.*,¹⁵ have shown that the photocatalytic activities for the oxidation of isopropanol on phthalocyanine-covered ZnO correlated with the oxidation potentials of the phthalocyanine.

We report here the photocatalyzed oxidation of hydroquinone by oxygen in the presence of phthalocyanine-coated TiO_2 powder in the anatase form. The phthalocyanine-coated TiO_2 catalysts were prepared as follows. The phthalocyanines, either metal-free (H_2Pc) or magnesium phthalocyanine (MgPc), were dissolved in N,N' -dimethylacetamide, TiO_2 (MCB reagent grade, particle size 125-250 μm) was added, the mixture stirred thoroughly and the solvent was then removed by evaporation. The reaction was studied with illumination from a 1.6 kW Xenon lamp with appropriate optical filters. The general procedure involved irradiation of 20 mL solution samples of 0.20 M Na_2SO_4 containing 2.0 mM hydroquinone and 0.200 g of photocatalyst in Pyrex tubes with continuous bubbling of oxygen. The amount of hydroquinone oxidized was determined by cyclic voltammetric analysis before and after irradiation. Typical results are given in Table 1. In control experiments 3 and 4 involving uncoated TiO_2 or H_2Pc -containing solutions irradiated with light of wavelength longer than 460 nm where TiO_2 shows no absorption but H_2Pc has strong absorption, very little oxidation of hydroquinone occurred. The photooxidation efficiency at long wavelengths (>460 nm) was, however, substantially enhanced by coating the phthalocyanines on TiO_2 powder (experiments 5 and 6). Accordingly, the photocatalytic activity at long wavelengths (>460 nm) is associated with the excitation of phthalocyanines and charge transfer at the interface between the phthalocyanine and TiO_2 , i.e., it is spectrally sensitized.

The photocatalytic activity of suspended phthalocyanine-coated TiO_2 powder can be correlated with the photoelectrochemical behavior of n -type TiO_2 (rutile) single crystal electrodes covered with phthalocyanine thin films. As shown in Fig. 1, the photoinduced oxidation of hydroquinone on an illuminated H_2Pc -coated TiO_2 electrode takes place at more negative potentials than the reduction of oxygen on the TiO_2 electrode. Thus, the photooxidation of hydroquinone on

phthalocyanine sites and the reduction of oxygen on TiO_2 sites can take place simultaneously on the same particle. As shown by the energy level scheme in Fig. 2, irradiation of an H_2Pc -coated TiO_2 particle with light of energy smaller than the band gap of TiO_2 but greater than the band gap of H_2Pc ($\sim 2 \text{ eV}$)¹⁶ causes excitation of an electron to the conduction band of H_2Pc leaving a hole in the valence band. The photogenerated holes are sufficiently energetic ($\sim 0.8 \text{ V vs. NHE}$)¹⁷ to oxidize hydroquinone while the photogenerated electrons are injected into the conduction band of TiO_2 leading to the reduction of oxygen.

Note that the photogenerated holes formed by the excitation of phthalocyanines are insufficiently energetic to oxidize H_2O or Cl^- . In the absence of hydroquinone or other reducing agents, the sensitized photocurrent showed a peak around -0.30 V vs. SCE (see curve c in Fig. 1) which decreased with time. This photocurrent is attributable to the photooxidation of phthalocyanines, which in the absence of reducing agents remains in the oxidized state. The addition of hydroquinone which acts as a "supersensitizer" is required to obtain a continuous current. The quantum efficiency for the photooxidation of hydroquinone at 632.8 nm under light intensity $\sim 50 \text{ mW/cm}^2$ was estimated to be about 0.1%. It is interesting to notice that different from the photocurrent peak shown in Fig. 1c for the H_2Pc -coated electrode, the peak photocurrent on the bare TiO_2 electrodes (d) was time-independent and was located at a slightly more positive potential (-0.22 V vs. SCE). The origin of this peak is not clear, but it probably involves the surface states of TiO_2 .

The experiments described here demonstrate the feasibility of sensitized photoassisted redox reactions with phthalocyanine-coated semiconductor powders. Sensitized heterogeneous photocatalytic and photoelectrosynthetic processes employing other semiconducting substrate powders and other phthalocyanines are currently under investigation in this laboratory.¹⁸

References and Notes

1. Frank, S. N.; Bard, A. J. J. Am. Chem. Soc. 1977, 99, 4667; Freund, T.; Gomes, W. P. Catal. Rev. 1969, 3, 1; Gerischer, H.; Roessler, H. Chem.-Ing. Tech. 1970, 42, 176; Nakatani, K.; Tsubomura, H. Bull. Chem. Soc. Jpn. 1977, 50, 783; Kraeutler, B.; Bard, A. J. J. Am. Chem. Soc. 1977, 99, 7729; Kraeutler, B.; Bard, A. J. J. Am. Chem. Soc. 1978, 100, 2239.
2. Gerischer, H.; Willig, F. Topics in Current Chem. 1976, 61, 31.
3. Gerischer, H. Photochem. Photobiol. 1972, 16, 243, and references therein.
4. Spitler, M. T.; Calvin, M. J. Chem. Phys. 1977, 66, 4294.
5. Miyasaka, T.; Watanabe, T.; Fujishima, A.; Honda, K. J. Am. Chem. Soc. 1978, 100, 6657.
6. Kim, H.; Laitinen, H. A. J. Electrochem. Soc. 1975, 122, 53.
7. Hawn, D.; Armstrong, N. R. J. Phys. Chem. 1978, 82, 1288.
8. Fujihira, M.; Osa, T. Nature 1976, 264, 349.
9. Meshitsuka, S.; Tamura, K. J. Chem. Soc. 1977, 73, 705.
10. Kommissarov, G. G. Russ. J. Phys. Chem., 1973, 47, 927; Kommissarov, G. G.; Shumov, Y. S.; Merozova, O. L. Biofizika 1970, 15, 1163.
11. Inoue, E.; Kokado, H.; Nakayama, T. Trans. Electron Dev. ED-19, 1972, 471.
12. Daltrozzo, E.; Tributsch, H. Photograph. Sci. Eng. 1975, 19, 308.
13. Memming, R. Photochem. Photobiol. 1972, 16, 325, and references therein; Gleria, M.; Memming, R. Z. Phys. Chem. (Frankfurt) 1975, 98, 303.
14. Clark, W. D. K.; Sutin, N. J. Am. Chem. Soc. 1977, 99, 4676.
15. Uchida, K.; Soma, M.; Onishi, T.; Tamaru, K. Z. Phys. Chem. Neue Folge 1977, 106, 317.
16. Gutman, F.; Lyons, L. E. "Organic Semiconductors," Wiley: New York, 1967.
17. Fan, F. R.; Faulkner, L. R., submitted to J. Am. Chem. Soc.

18. The support of this research, which is a joint project with Professor A. B. P. Lever of York University, by the Office of Naval Research is gratefully acknowledged.

Fu-Ren F. Fan, Allen J. Bard
Department of Chemistry
The University of Texas at Austin
Austin, Texas 78712

Table 1. Sensitized Photocatalytic Oxidation of Hydroquinone in Oxygen-Saturated Solutions^a

Exp. No.	Catalyst ^b	Time of Illumination (hrs)	Illumination Wavelengths	Hydroquinone Oxidized, (%)
1	TiO ₂ (anatase)	4.0 ^c	white light	< 1
2	TiO ₂ (anatase)	4.0	white light	52
3	H ₂ Pc	23.0	> 460 nm	1
4	TiO ₂ (anatase)	22.0	> 460 nm	3
5	TiO ₂ (anatase)/H ₂ Pc ^d	22.5	> 460 nm	25
6	TiO ₂ (anatase)/MgPc ^d	23.0	> 460 nm	17

^a 20 mL of 0.20 M Na₂SO₄ containing 2.0 mM hydroquinone.

^b 200 mg. TiO₂ taken.

^c Solution was deoxygenated thoroughly with N₂.


^d TiO₂ was partially coated with about 2 mg. of the phthalocyanine from N,N'-dimethylacetamide solution.

Figure Captions

Fig. 1 Current-potential curves for n-type TiO_2 (rutile, single crystal) and metal-free phthalocyanine-coated n-type TiO_2 electrodes in the dark and under chopped illumination with 450 W Xe lamp fitted with a 590 nm cut-on filter. Curves a and b use the right-hand scale and curves c-e use the left-hand scale. The photocurrent was measured by phase-sensitive detection techniques. Cyclic voltammetry in the dark at TiO_2 in (a) deoxygenated and (b) oxygen-saturated 0.25 M Na_2SO_4 , 0.025 M phosphate buffer (pH \approx 6.9). Scan rate, 100 mV/sec. Initial potential +0.60 V vs. SCE. (c) Current potential curve under illumination at H_2Pc -coated TiO_2 electrodes in deoxygenated 0.25 M Na_2SO_4 , 0.025 M phosphate buffer (pH \approx 6.9) or 0.50 M KCl, 0.025 M phosphate buffer (pH \approx 6.9). H_2Pc film thickness $\sim 500 \text{ \AA}$. Scan rate, 5 mV/sec. Initial potential -0.37 V vs. SCE. (d) Current-potential curve under illumination at TiO_2 in deoxygenated 0.25 M Na_2SO_4 , 0.025 M phosphate buffer (pH \approx 6.9) with or without 0.50 mM hydroquinone. Scan rate, 5 mV/sec. Initial potential -0.28 V vs. SCE. (e) Current-potential curve under illumination at H_2Pc -coated TiO_2 electrodes in deoxygenated 0.25 M Na_2SO_4 , 0.025 M phosphate buffer (pH \approx 6.9) containing 0.50 mM hydroquinone. H_2Pc film thickness $\sim 500 \text{ \AA}$. Scan rate, 5 mV/sec. Initial potential -0.45 V vs. SCE. s denotes the potential at which the scan was initiated.

Fig. 2 Schematic diagram for the electron transfer at H_2Pc on TiO_2 . E_{CB} and E_{VB} denote the potentials of the conduction band edge and the valence band edge of TiO_2 . E_{CB}' and E_{VB}' are the corresponding potentials for H_2Pc . Redox potential for p-hydroquinone (H_2Q)/p-benzoquinone (BQ) is shown on the right.

Fig. 1

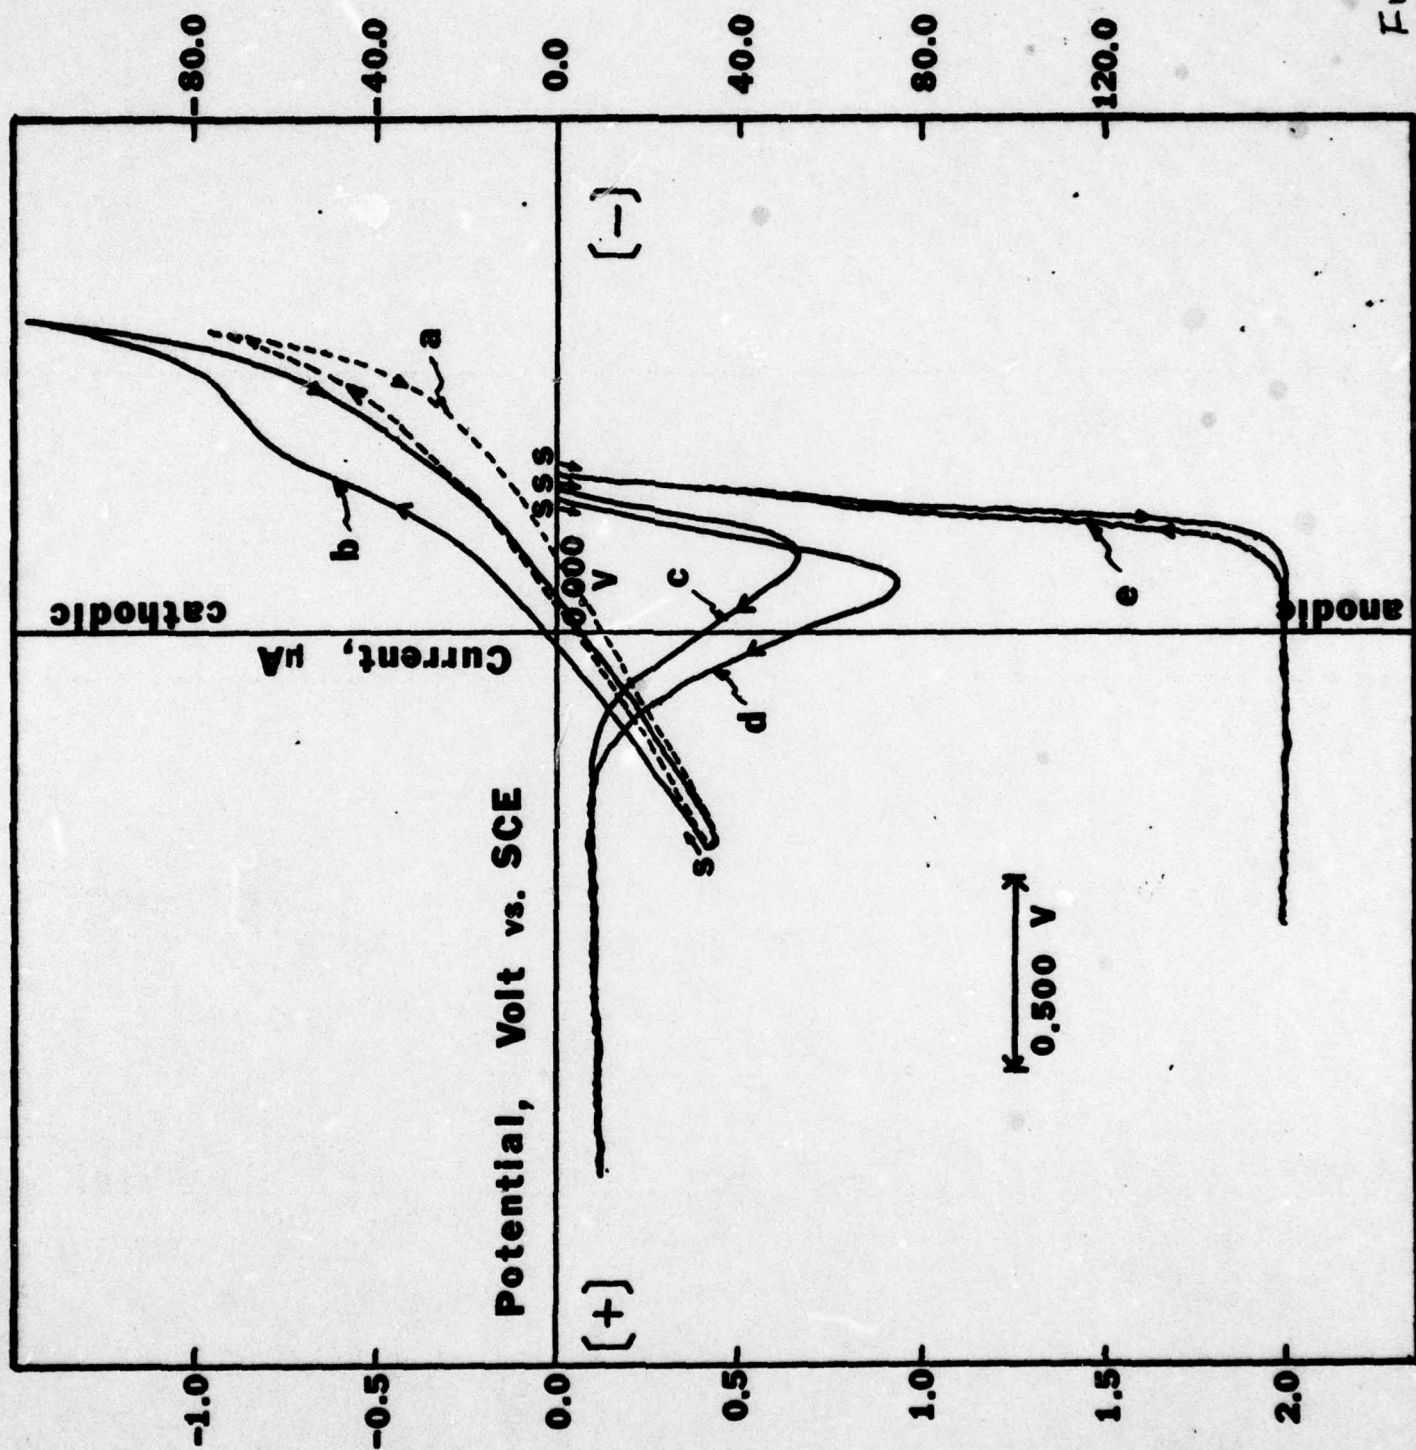

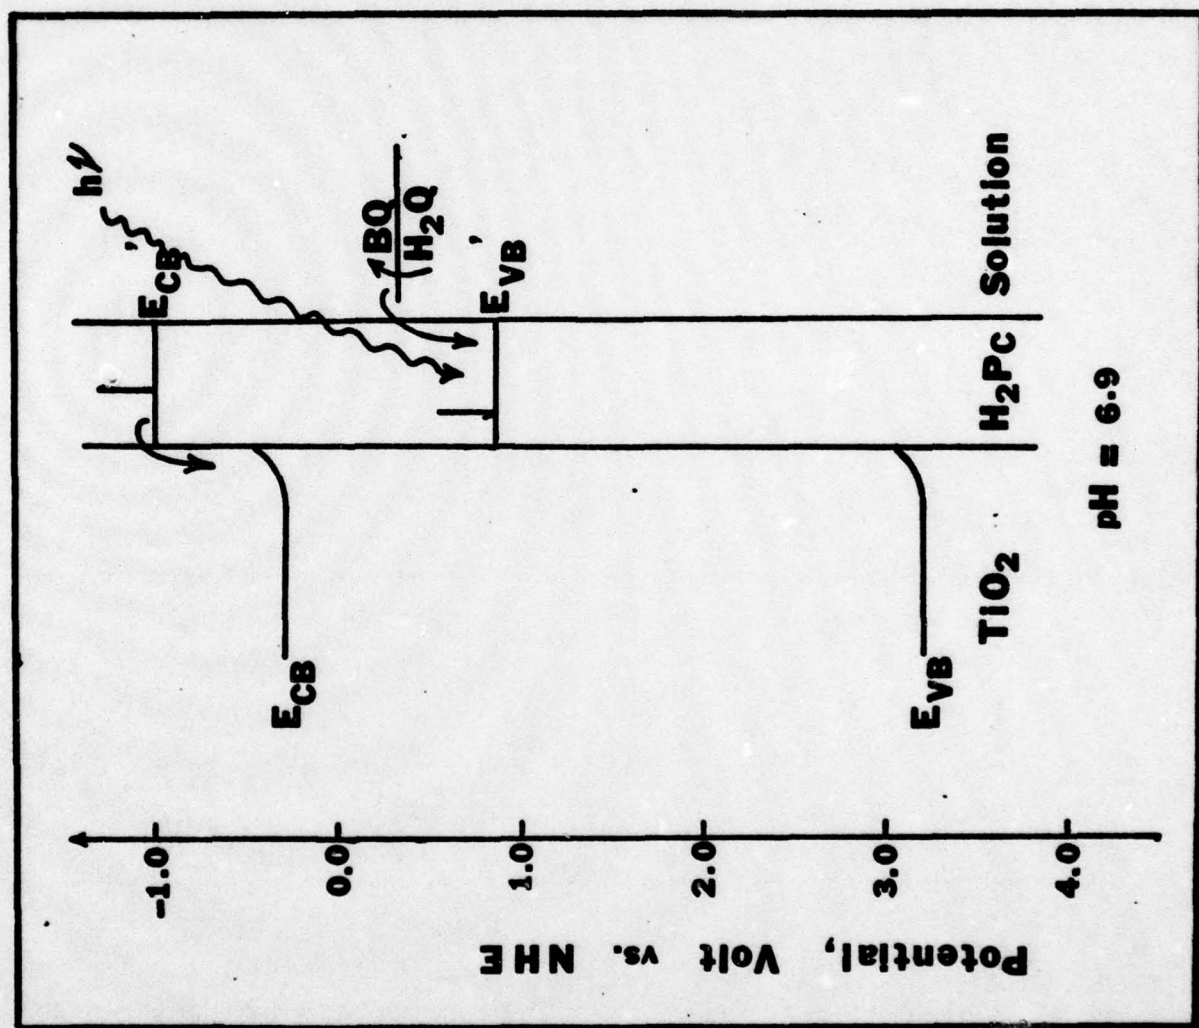


Fig. 2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research 800 North Quincy Street Arlington, Virginia 22217 Attn: Code 472	2	Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12
ONR Branch Office 536 S. Clark Street Chicago, Illinois 60605 Attn: Dr. George Sandoz	1	U.S. Army Research Office P.O. Box 1211 Research Triangle Park, N.C. 27709 Attn: CRD-AA-IP	1
ONR Branch Office 715 Broadway New York, New York 10003 Attn: Scientific Dept.	1	Naval Ocean Systems Center San Diego, California 92152 Attn: Mr. Joe McCartney	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106 Attn: Dr. R. J. Marcus	1	Naval Weapons Center China Lake, California 93555 Attn: Dr. A. B. Amster Chemistry Division	1
ONR Area Office One Hallidie Plaza, Suite 601 San Francisco, California 94102 Attn: Dr. P. A. Miller	1	Naval Civil Engineering Laboratory Port Hueneme, California 93401 Attn: Dr. R. W. Drisko	1
ONR Branch Office Building 114, Section D 666 Summer Street Boston, Massachusetts 02210 Attn: Dr. L. H. Peebles	1	Professor K. E. Woehler Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Washington, D.C. 20390 Attn: Code 6100	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (R,E&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research 800 N. Quincy Street Arlington, Virginia 22217 Attn: Dr. Richard S. Miller	1
Commander, Naval Air Systems Command Department of the Navy Washington, D.C. 20360 Attn: Code 310C (H. Rosenwasser)	1	Naval Ship Research and Development Center Annapolis, Maryland 21401 Attn: Dr. G. Bosmajian Applied Chemistry Division	1
		Naval Ocean Systems Center San Diego, California 91232 Attn: Dr. S. Yanamoto, Marine Sciences Division	1

Encl 1

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. Paul Delahay New York University Department of Chemistry New York, New York 10003	1	Library P. R. Mallory and Company, Inc. Northwest Industrial Park Burlington, Massachusetts 01803	1
Dr. R. A. Osteryoung Colorado State University Department of Chemistry Fort Collins, Colorado 80521	1	Dr. P. J. Hendra University of Southampton Department of Chemistry Southampton SO9 5NH United Kingdom	1
Dr. E. Yeager Case Western Reserve University Department of Chemistry Cleveland, Ohio 41106	1	Dr. Sam Perone Purdue University Department of Chemistry West Lafayette, Indiana 47907	1
Dr. D. N. Bennion University of California Chemical Engineering Department Los Angeles, California 90024	1	Dr. Royce W. Murray University of North Carolina Department of Chemistry Chapel Hill, North Carolina 27514	1
Dr. R. A. Marcus California Institute of Technology Department of Chemistry Pasadena, California 91125	1	Naval Ocean Systems Center San Diego, California 92152 Attn: Technical Library	1
Dr. J. J. Auburn Bell Laboratories Murray Hill, New Jersey 07974	1	Dr. J. H. Ambrus The Electrochemistry Branch Materials Division, Research & Technology Department Naval Surface Weapons Center White Oak Laboratory Silver Spring, Maryland 20910	1
Dr. Adam Heller Bell Telephone Laboratories Murray Hill, New Jersey 07974	1	Dr. G. Goodman Globe-Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. T. Katan Lockheed Missiles & Space Co, Inc. P.O. Box 504 Sunnyvale, California 94088	1	Dr. J. Boechler Electrochimica Corporation Attention: Technical Library 2485 Charleston Road Mountain View, California 94040	1
Dr. Joseph Singer, Code 302-1 NASA-Lewis 21000 Brookpark Road Cleveland, Ohio 44135	1	Dr. P. P. Schmidt Oakland University Department of Chemistry Rochester, Michigan 48063	1
Dr. E. Brummer EIC Incorporated Five Lee Street Cambridge, Massachusetts 02139	1		

TECHNICAL REPORT DISTRIBUTION LIST, 359

	<u>No. Copies</u>
Dr. H. Richtol Chemistry Department Rensselaer Polytechnic Institute Troy, New York 12181	1
Dr. A. B. Ellis Chemistry Department University of Wisconsin Madison, Wisconsin 53706	1
Dr. M. Wrighton Chemistry Department Massachusetts Institute of Technology Cambridge, Massachusetts 02139	1
Larry E. Plew Naval Weapons Support Center Code 3073, Building 2906 Crane, Indiana 47522	1
S. Ruby DOE (STOR) 600 E Street Washington, D.C. 20545	1
Dr. Aaron Wold Brown University Department of Chemistry Providence, Rhode Island 02192	1
Dr. R. C. Chudacek McGraw-Edison Company Edison Battery Division Post Office Box 28 Bloomfield, New Jersey 07003	1
Dr. A. J. Bard University of Texas Department of Chemistry Austin, Texas 78712	1
Dr. M. M. Nicholson Electronics Research Center Rockwell International 3370 Miraloma Avenue Anaheim, California 92803	1
Dr. M. G. Sceats University of Rochester Department of Chemistry Rochester, New York 14627	1